

Novel Grafting Procedure of Ruthenium 2,2':6',2''-Terpyridine Complexes with Phosphonate Ligands to Titania for Water Splitting Applications

Marcus Waser^a, Christian Siebenhaar^a, Jennifer Zampese^b, Gerhard Grundler^a, Edwin Constable^b, Murray Height^c, and Uwe Pieles^{*a}

*Correspondence: Prof. Dr. U. Pieles^a, Tel.: +41 61 467 4453, Fax: +41 61 467 4457
E-mail: uwe.pieles@fhnw.ch

^aUniversity of Applied Sciences Northwestern Switzerland, School of Life Sciences, Institute for Chemistry and Bioanalytics, Gründenstrasse 40 CH-4132 Muttenz

^bDepartment of Chemistry, University of Basel

^cHeiQ Materials, Bad Zurzach

Keywords: Ruthenium terpyridine complexes · Phosphonic acid linkers · Titanium dioxide grafting

Introduction

Power needs and the demand for carbon-neutral energy sources are growing both nationally and internationally. These challenges could be overcome simultaneously by the use of water-splitting cells in which sunlight is used as a sustainable energy source and hydrogen for chemical energy storage.

Sunlight-assisted electrolysis of water was first reported in 1972 by Fujishima and Honda^[1] using TiO₂ as photoanode and platinum as cathode. One problem of using pure TiO₂ as photoanode is that only the ultraviolet part of the solar spectrum is absorbed due to the large band gap of 3–3.2 eV. Other semiconductors with band gaps able to absorb the visible part of the spectrum are unstable against photo corrosion. A solution to this complexity was found when the TiO₂ was dye-sensitized with a coloured material possessing a ground state below and an excited state above the conduction band of the semiconductor. By dye-sensitizing, visible light is absorbed by the dye which forms a molecular excited state and the excited state may then inject an electron into the TiO₂ conduction band causing charge separation. In the case of dye-sensitized solar cells confirmed efficiencies of >10% have been reported.^[2] Because of the operating requirements of long-term stability in the presence of air, water and other additives in the system, metal-containing dyes are usually preferred over purely organic materials. Particular emphasis has been placed on the use of ruthenium dyes, which absorb from the green through to the near IR in some cases, containing oligopyridine ligands.

In order to produce a commercial product for the splitting of water, the production steps leading to the final product must be addressed. The dye used for sensitisation has to be produced and grafted onto the TiO₂ in as few steps as possible. Commonly the grafting is done by reacting a carboxylic or phosphonic acid group of the dye with TiO₂. We are particularly interested in phosphonic acid linkers and the conventional synthetic route involves conversion of the phosphonate ester to the phosphonic acid which is then used to graft onto the TiO₂. By using the phosphonic ester to graft directly onto the TiO₂, one reaction step could be avoided. Direct grafting of phosphonate esters onto different metal ox-

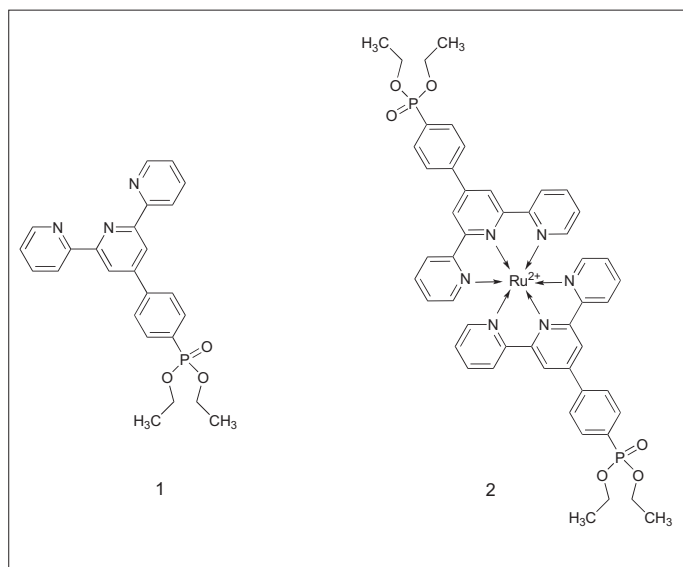


Fig. 1. Phosphonate ligand and the corresponding ruthenium dye for functionalisation of TiO₂.

ides including TiO₂ has been described earlier.^[3] We selected 2,2':6',2''-terpyridine ligands containing phosphonate substituents in the first instance and describe here results with ligand **1** and the ruthenium dye **2** (Fig. 1).

Results and Discussion

Conventional functionalisation methods for TiO₂ involve direct reaction with a complex bearing carboxylic acid or phosphonic acid functionality. The purification and characterisation of these species is often difficult because of i) uncertainties over the protonation state of the substituents and ii) the high water solubility. It is attractive to avoid the preparation of the free phosphonic acid species and we have now shown that it is possible to functionalise the TiO₂ surface with either **1** or **2**. Although **1** is colourless, we have developed convincing visual proof that the phosphonate ester can be grafted directly onto TiO₂. The grafting was carried out using the procedure of Frantz *et al.*^[3a] in which the ligand **1** is dissolved in 2-propanol and refluxed for five days with the TiO₂. The excess of ligand is separated by centrifugation and repeated washing. 2,2':6',2''-Terpyridine ligands form stable and highly coloured [FeL₂]²⁺ complexes with iron(II) salts. The complexes are purple with an absorption maximum typically close to 550 nm. When solutions of iron(II) salts are added to the functionalised TiO₂ slurry, an immediate purple colour develops. The purple colour develops only on the solid and not in the supernatant establishing i) that the surface of the TiO₂ has been modified with **1** and ii) that the complexes are irreversibly bound to the surface of the semiconductor.

Grafting of the dye **2** onto the surface proved to be more delicate. Using the same procedure as before, it took three weeks to graft only a very small amount of dye onto titania (weight ratio dye/titania 1:100). The unfavourable reaction time could be

improved by carrying out the reaction under microwave heating. Several solvents and reaction conditions were tested for optimal surface modification. Of all the solvents tested, ethane-1,2-diol and also 1-butanol showed the best results. The yield using the ester complex **2** is not yet as high as when the corresponding acid is used for the reaction but the advantages in material preparation and characterisation are manifest. In the case of 1-butanol as a solvent, at high concentrations of **2** an insoluble ruthenium species is formed that we suspect is the zwitterionic complex of the monoester ligand.

In conclusion, we have found a viable alternative to the preparation of free phosphonic acids for the preparation of dye sensitised solar cells. We also note the subsequent metallation of the TiO₂ modified with **1** should also lead to novel functional materials.

Received: March 24, 2010

-
- [1] A. Fujishima, K. Honda, *Nature* **1991**, 353, 737.
[2] M. Green, K. Emery, Y. Hishikawa, W. Warta, *Prog. Photovoltaics: Res. App.* **2008**, 16, 61.
[3] a) R. Frantz, J.-O. Duranda, M. Graniera, G.F. Lanneau, *Tetrahedron Lett.* **2004**, 45, 2935; b) G. Guerrero, P. H. Mutin, E. Framery, A. Vioux, *New J. Chem.* **2008**, 32, 1519; c) G. Guerrero, P. H. Mutin, E. Framery, A. Vioux, *Chem. Mater.* **2001**, 13, 4367.